

NAB/UV-1K AC



VUDAC IMPREGNANTS

Characteristic

NAB/UV-1K AC is a single component impregnating resin with medium viscosity based on unsaturated polyester-imide resin dissolved in diacrylate with photoinitiators. Compared to other acrylic impregnating resins, it has improved anti-corrosion properties. It has a clear amber look and is odorless. There is little emission (VOC) released during curing. Does not pollute the work environment, does not create a fire hazard. Waste air does not need to be cleaned.

Impregnation is characterized by the following properties:

- Excellent resistance to corrosion and moisture
- Excellent thermal resistance
- Excellent mechanical strength
- Cleanliness of system surfaces after impregnation
- Perfect build-up and penetration into the windings
- Minimal cure losses
- Exceptional cure efficiency
- Customizable processing properties according to customer requirements

Field of application

NAB/UV-1K AC is suitable for applications in temperature class H. It is designed for the impregnation of windings of electric rotary machines of general use and transformers. Electric machines wound with large diameter varnished wires and large cross section profile wires, where anticorrosive treatment is required

Processing

NAB/UV-1K AC is specially developed for impregnation by immersion on an impregnating device with combined curing, electric current and UV radiation. The impregnation can also be processed on conventional impregnation devices at atmospheric pressure or vacuum by dipping, flooding or widening under rotation. Exact instructions for processing will be provided depending on the customer's processing method.

Since it is a one-component system, additional additives are not required before use. During processing, it is essential to limit as much as possible light access to the impregnating resin in impregnating tank. The recommended impregnant change in the tank is 20% of the total volume per month. To achieve the maximum lifetime of the impregnant, its recommended to maintain operating temperature 25°C as maximum.

When handling the impregnating resin, follow the safety instructions in the Safety Data Sheet.

To clean the equipment and work tools from undamaged impregnant it is recommended to use VUKI thinner T5.

Hardening

Curing conditions:

- combined curing by electric current and UV radiation: 10 – 20 min at 150 ÷ 180 °C and 12 ÷ 16 min UV radiation depending on the power of the UV emitter
- conventional curing: 2 – 3 h from reaching 130 °C in the winding




NAB/UV-1K AC



VUDAC IMPREGNANTS

Processing properties

Parameter	Standard	Condition	Value	Unit	Description
Density	STN EN ISO 2811-1	20 °C	1050 – 1150	kg/m ³	
Viscosity	STN 67 3014	25 °C	2000 – 3000	mPa.s	value adjustable according to customer request
Flash point	STN EN ISO 2592		> 110	°C	
Gel time	DIN 16 945	100 °C 130 °C	12 – 16 2/30 – 5	min	
Reaction time	STN EN 60455-2	130 °C	3 – 6	min	
Exothermic temperature	STN EN 60455-2	130 °C	190 – 230	°C	
VOC			< 2	%	
Hardening time		130°C in a conventional manner	2 – 3	h	from reaching a temperature of 130°C in the winding
		150 – 180°C UV radiation	10 – 20 12 – 16	min	combined mode: temperature and UV radiation
Effect on enameled wires	STN EN 60851-4,5 STN EN 60317		suitable		compatible with all commonly used wires

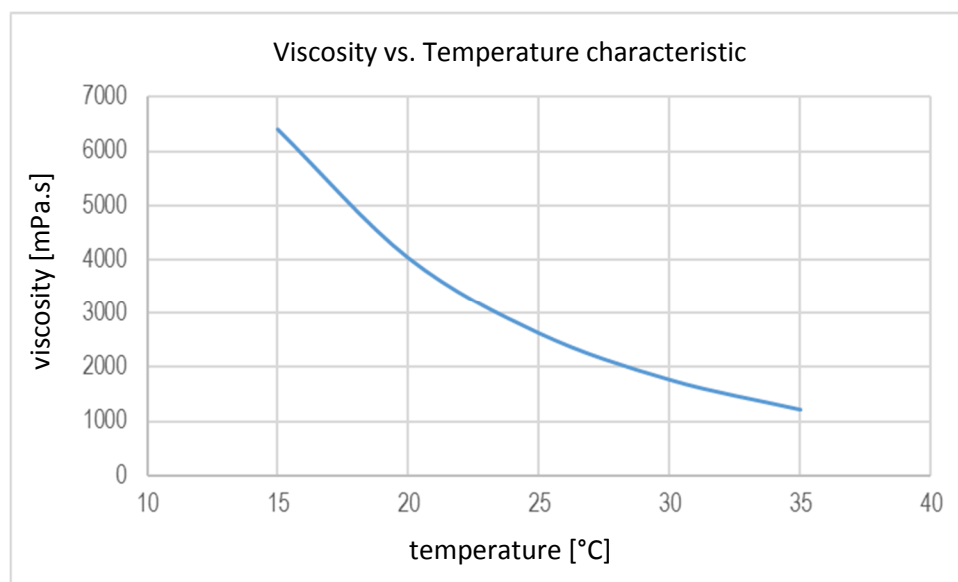

NAB/UV-1K AC



VUDAC IMPREGNANTS

Parameters after hardening

Parameter	Standard	Condition	Value	Unit	Description
Drying in thick layer	STN EN 60464-2	1 h at 100 °C + 1 h at 150 °C	I 1.1 S1 U1		sample solid, no cracks and bubbles, surface smooth, non-stick
Layer thickness on AL sheet			24	µm	
Electrical strength	STN EN 60243-1	23 °C 180 °C after 24 h immersed in water at 23 °C	80 65 50	kV/mm	cylindrical electrodes ø 6 mm
Volume resistivity	STN EN 62631-3-1	23 °C 155 °C 180 °C after 168 h immersed in water at 23 °C	10 ¹⁴ 10 ⁹ 10 ⁸ 10 ¹³	Ω.m	
Relative permittivity	STN EN 60455-2	25 °C/500V 180°C/500V	3,76 5,8	-	
Dielectric dissipation factor tg δ	STN EN 60455-2	25 °C/500V 180°C/500V	0,0135 0,5	-	
Twisted coil strength	STN EN 61 033 art. 2.1 method A	23 °C 180 °C	190 – 220 80 – 100	N	
Temperature index	STN IEC 60 216		180	°C	

Packing, storing and manipulation

Impregnating resin is supplied in non-returnable, clean, metal drums with weight 200 kg or in black IBC containers with weight 1000kg. Alternatively, other packaging can be used according agreement. Impregnating resin is stored in tightly closed containers in a dry, ventilated place at + 5 ° C to + 25 ° C. When the storage conditions are met, the quality of the impregnating resin is guaranteed 12 months from the date of manufacture. **Impregnation must not be exposed to light!**

CAUTION: Extreme heat, contamination or exposure to direct sunlight may result in the polymerization and deterioration of the impregnant!

Impregnating resin is not classified as a dangerous product.

Certificates

- twisted pairs: 180 °C, teplotná trieda H (UL file E233982)
- helical coils: 180 °C, teplotná trieda H (UL file E233982)

NOTE

The information in this document is consistent with our best knowledge of the date of publication. This information can be a subject of revision without prior notice if new knowledge and experience are available. The data provided falls within the normal range of product properties and relates only to the specified material. These data may not apply to materials used in combination with other materials or ingredients or other processes, unless expressly stated otherwise. The data provided should not be used to set limits or used separately as a basis for the sample: they are not intended to compensate for any testing that may be necessary to make a decision as to whether the specific material is suitable for your particular purpose. Because VUKI cannot predict all variants of end-use product conditions, VUKI does



NAB/UV-1K AC



VUDAC IMPREGNANTS

not provide guarantees and has no responsibility with respect to any use of this information. Nothing in this publication is considered to be a use or recommendation to violate any patent rights.

Contact

VUKI a.s., Rybníčná 38, 831 07 Bratislava 06
Customer service – tel.: +421 906 063 231, +421 906 063 107
e-mail: info@vuki.sk
<http://www.vuki.sk>

Version

2019-06-10



VUKI a.s., Rybníčná 38, SK - 831 07 Bratislava, Tel.: +421 906 063 231
e-mail: vuki@vuki.sk, www.vuki.sk